

# Modulating the Optoelectronic Properties of Tripodal Fluorophores through Fluorine-Substituted Peripheral Phenyls

Milan Klikar,<sup>\*[a]</sup> Eva Prokopová,<sup>[a]</sup> Lefteris Laleas,<sup>[b]</sup> Giorgos Soutse,<sup>[b]</sup> Alexandros Katsidas,<sup>[b]</sup> Zdeňka Růžičková,<sup>[c]</sup> Zuzana Burešová,<sup>[a]</sup> Oldřich Pytela,<sup>[a]</sup> Filip Bureš,<sup>[a]</sup> and Mihalis Fakis<sup>[b]</sup>

[a] Dr. M. Klikar, E. Prokopová, Dr. Z. Burešová, Prof. O. Pytela, Prof. F. Bureš

Institute of Organic Chemistry and Technology  
Faculty of Chemical Technology, University of Pardubice  
Studentská 573, Pardubice, 53210, Czechia

E-mail: [milan.klikar@upce.cz](mailto:milan.klikar@upce.cz)

[b] L. Laleas, G. Soutse, A. Katsidas, Prof. M. Fakis

Department of Physics  
University of Patras  
Patras, 26504, Greece

[c] Dr. Z. Růžičková

Department of General and Inorganic Chemistry  
Faculty of Chemical Technology, University of Pardubice  
Studentská 573, Pardubice, 53210, Czechia

Supporting information for this article is given via a link at the end of the document.

**Abstract:** Fourteen novel tripodal fluorophores based on a central triphenylamine donor, electron-rich and polarizable divinylthiophene linker, and eight different fluorine-based substituents have been designed and prepared via a straightforward four-step sequence. Altering the peripheral F-substitution has been demonstrated to largely affect their fundamental properties such as thermal robustness (210–420 °C), the LUMO energies ( $E_{\text{LUMO}} = -2.35$  to  $-3.11$  eV), the HOMO–LUMO gap ( $\Delta E = 2.07$ – $2.66$  eV), and the absorption/emission maxima ( $\lambda_{\text{max}}^{\text{A/E}} = 442$ – $478/521$ – $678$  nm). The experimental data, corroborated by DFT calculations, further revealed twofold and tunable ICT employing both central triphenylamine and auxiliary thiophene donors, and the peripheral F-substitution either boosting or switching-off two-photon absorption activity. Whereas the  $-\text{SF}_5$  groups impart an exceptional cross-section of 1930 GM, the  $-\text{COCF}_3$  group may completely suppress the nonlinear optical response.

## Introduction


The last couple of decades has demonstrated triphenylamine (TPA) as a robust electron-donating building block widely utilized in the modular construction of push-pull D- $\pi$ -A chromophores (D = electron-donor,  $\pi$  = conjugated system and A = electron-acceptor) with numerous applications across optoelectronics.<sup>[1,2]</sup> This situation stems from its direct synthetic availability, good electron-donating and transporting capability, hole-transporting properties, and facile functionalization.<sup>[3]</sup> The propeller-shaped arrangement predisposes TPA to building octupolar chromophores with the centrifugal D-( $\pi$ -A)<sub>3</sub> architecture featuring various  $\pi$ -branches and diverse peripheral electron-acceptors.<sup>[4]</sup> Due to strong electronic coupling between the individual branches, tripodal TPA chromophores generally possess exceptional hyperpolarizability and a two-photon absorption (2PA) cross-section<sup>[3,5–9]</sup> that have been utilized across materials science, biology, and medicine.<sup>[10–12]</sup> Two-photon fluorescence microscopy,<sup>[13]</sup> 2PA fluorescence cellular imaging,<sup>[14–17]</sup> and photodynamic therapy<sup>[18–21]</sup> have become routinely employed noninvasive biomedical methods, while microfabrication,<sup>[22–24]</sup> 3D data storage,<sup>[25,26]</sup> and up-converted lasing<sup>[27]</sup> represent prominent material applications.

Fluorine is a relatively small atom with the highest electronegativity and low polarizability. It forms a high-energy C–F bond ( $\approx 480$  kJ·mol<sup>-1</sup>), which is strategically used to improve chemical and thermal stability of (per)fluorinated organic compounds as well as to modulate their biological activity. In this respect, fluorination primarily improves cell permeability, lipophilicity, solubility, and other pharmacological parameters.<sup>[28,29]</sup> Furthermore, the strongly polarized C–F bond may affect molecular geometry, charge/electron distribution, and specific non-covalent interactions such as C–F $\cdots$ H hydrogen bonding or  $\pi$ - $\pi^{\text{F}}$  interactions.<sup>[30–32]</sup> Appending fluorine atom(s) to a  $\pi$ -conjugated system substantially alters the electronic distribution and allows tuning of the HOMO/LUMO levels and semiconducting properties. Numerous reports have demonstrated enhanced performance and characteristics of fluorinated organic materials over their non-fluorinated analogues,<sup>[33]</sup> e.g.

## RESEARCH ARTICLE

pronounced nonlinear optical (NLO) activity.<sup>[30–32]</sup> Single- ( $\sigma_p(\text{F}) = 0.06$ ), perfluoro- or trifluoromethyl-substituted ( $-\text{CF}_3$ ;  $\sigma_p = 0.35$ ) push-pull systems are among the most widely utilized strategies.<sup>[28,29]</sup> In contrast, the octahedral pentafluorosulfanyl<sup>[34]</sup> ( $-\text{SF}_5$ ;  $\sigma_p = 0.68$ ) is much less employed, while the trifluoroacetyl ( $-\text{COCF}_3$ ;  $\sigma_p = 0.80$ ) is a relatively scarce electron-acceptor.<sup>[35–37]</sup> Trifluoromethoxy ( $-\text{OCF}_3$ ;  $\sigma_p = 0.35$ ), trifluorosulfanyl ( $-\text{SCF}_3$ ;  $\sigma_p = 0.50$ ), and trifluoromethyl sulfone ( $-\text{SO}_2\text{CF}_3$ ;  $\sigma_p = 0.96$ ) are known substituents in agrochemicals or pharmaceuticals.<sup>[38–40]</sup> The listed Hammett substituent constants ( $\sigma_p$ ) allow a rough evaluation of the electronic effects and point out the trifluoromethyl sulfone and trifluoroacetyl as very potent acceptors, superior to the common nitro group ( $\sigma_p = 0.78$ ).<sup>[41]</sup> While the moderate withdrawing strength of the  $-\text{CF}_3$  and  $-\text{SF}_5$  substituents stems from negative inductive effects and eventual hyperconjugation, the  $-\text{COCF}_3$  or  $-\text{SO}_2\text{CF}_3$  substituents combine negative mesomeric and inductive effects. In addition, the less withdrawing  $-\text{OCF}_3$  and  $-\text{SCF}_3$  groups oscillate orthogonally to the appended aryl ring, thereby affecting  $\pi$ -conjugation and electron distribution differently from the tetrahedral  $-\text{CF}_3$  substituent.<sup>[38,42]</sup>

Figure 1A summarizes the reported TPA chromophores bearing (poly)fluorinated acceptors **A–F**. Gradually fluorinated benzenes have been used as peripheral acceptors in TPA derivatives **A1–5** and **C1**, which proved useful as blue-violet emitters or hole-transporters of OLEDs.<sup>[43]</sup> Even better OLED characteristics were measured for pentafluorophenyl derivatives **B1** and **B3**,<sup>[44]</sup> while **B1** also showed noticeable third-order optical nonlinearity.<sup>[3,45]</sup> The pentafluorophenylethynyl pendant in **B2** allowed a substantial singlet oxygen production upon two-photon excitation.<sup>[46]</sup> Bis(trifluoromethyl) derivative **C2** has been reported as a moderate luminophore for luminescent solar concentrators<sup>[47]</sup> and  $\text{CF}_3$ -capped cyanostilbenes **C3–C4** are AIEgens forming stable organogels.<sup>[48]</sup> The first pentafluorosulfanyl-terminated TPA chromophore **D1**, reported in 2018 by Gautam et al., demonstrated a large 2PA cross-section reaching 2000 GM,<sup>[49]</sup> verifying the  $\text{SF}_5$  group as a potent electron-withdrawing unit for efficient multiphoton absorbers. This year, we further demonstrated a selective employment of the electronic effects of the  $\text{SF}_5$  group in a series of tripodal fluorophores **D2–D3**. The  $\text{SF}_5$  group placed in the *para* position allows hyperconjugation with the TPA donor and imparts **D2** a 2PA cross-section of 600 GM.<sup>[50]</sup> The trifluoroacetyl-substituted derivative **E1** is capable of sensing amines,<sup>[51]</sup> while the strongly withdrawing trifluoromethyl sulfone has been investigated by the research team of M. Blanchard-Desce.<sup>[52–55]</sup> Property tuning in **F1–F7** was achieved by altering the  $\pi$ -system, while the olefinic linker turned out to be more efficient as compared to the acetylenic one. When comparing **F4** and **F5**, the latter showed two-fold increase in the 2PA activity, reaching 2000 GM. A comparison of the fluorinated sulfone and sulfoximiny groups in **F2** and **F3** reveals the  $\text{SO}(\text{NSO}_2\text{CF}_3)\text{CF}_3$  group as “superacceptor” with the  $\sigma_p = 1.35$  and enhanced 2PA activity (500 vs. 870 GM).

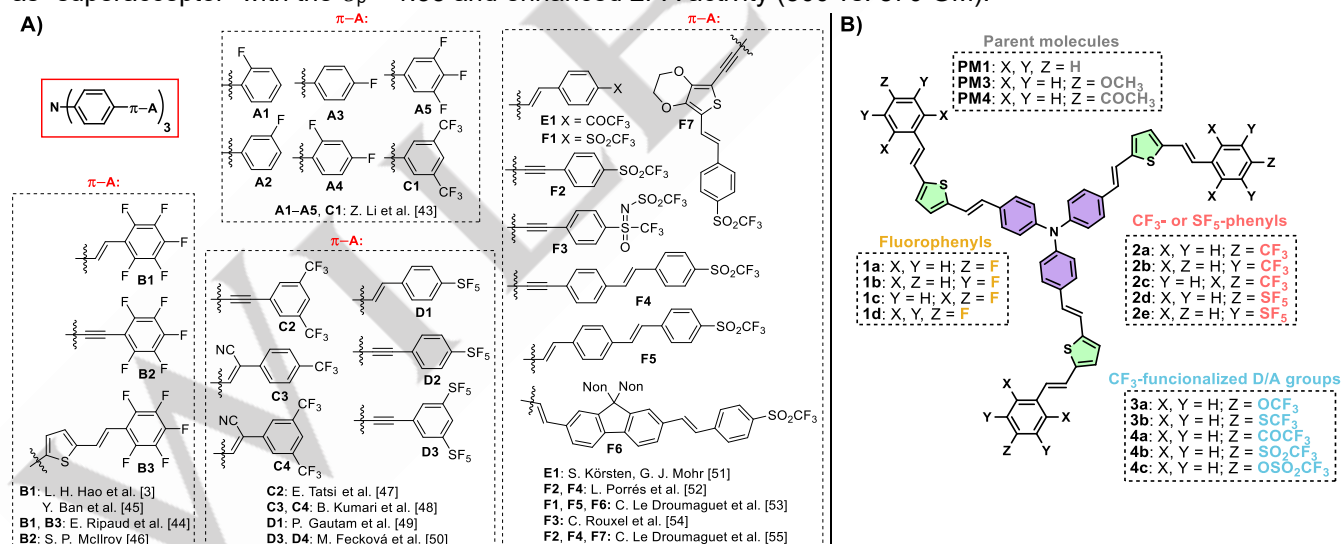

**Figure 1.** A) Known tripodal TPA chromophores bearing varied  $\pi$ -system and fluorine-based acceptors; B) Investigated tripodal TPA-based fluorophores in this work.

Despite increasing popularity, the current state-of-the-art lacks a systematic study comprehensively comparing fluorine-based substituents and their impact on the fundamental optoelectronic properties of push-pull molecules, while only fragmented and limited reports available to date.<sup>[56–58]</sup> Hence, based on our continuing interest in octupolar fluorophores with 2PA activity<sup>[59–63]</sup> and following our recent study on  $\text{SF}_5$ -terminated TPA fluorophores,<sup>[50]</sup> we present herein an extensive series of  $\text{C}_3$ -symmetric push-pull molecules **1–4** (Fig. 1B). These designed systems feature varying numbers (1–5) of the fluorinated groups at the periphery ( $-\text{F}$ ,  $-\text{CF}_3$ ,  $-\text{SF}_5$ ,  $-\text{OCF}_3$ ,  $-\text{SCF}_3$ ,  $-\text{COCF}_3$ ,  $-\text{SO}_2\text{CF}_3$ , and  $-\text{OSO}_2\text{CF}_3$ ) placed at different position along the periphery (*ortho*, *meta*, *para*) to systematically investigate their optoelectronic properties. The central TPA donor and the peripheral acceptors are interconnected


## RESEARCH ARTICLE

via a novel, highly polarizable 2,5-divinylthiophene  $\pi$ -linker possessing thiophene as an auxiliary donor, which is introduced into TPA chromophores for the first time. Both vinylene spacers enforce planarity, assure efficient intramolecular charge transfer (ICT), and, supposedly, also enhance 2PA activity. In addition, we present a series of parent molecules **PM1–3** and one linear analogue **2aL** to properly address the effect of fluorination and branching. The fundamental chemical, thermal, electrochemical, photophysical, and (non)linear optical properties of **1–4** and **PM1–3** were further corroborated by quantum-chemical calculations.

## Results and Discussion

## Synthesis

To synthesize all target fluorophores **PM1–3** and **1–4** in a straightforward manner, four synthetic steps involving Suzuki-Miyaura cross-coupling (2 $\times$ ), selective bromination, and Heck olefination were employed (Scheme 1C). The substituted iodo- or bromobenzenes **10–14** (Scheme 1B) were used to introduce the fluorinated acceptors; intermediates **12c**, **12d**, and **9** were prepared according to the modified literature procedures (see the SI for more details).<sup>[52,64,65]</sup> (*E*)-2-(Thiophen-2-yl)ethenylboronic acid pinacol ester **7**, a key intermediate allowing the facile and systematic construction of each branch, was smoothly prepared from 2-bromothiophene **5** and the vinylboronic acid pinacol ester **6** via a Pd-catalyzed Heck olefination in 93% yield (Scheme 1A).<sup>[66]</sup> The fluorinated acceptors **10–14** were first cross-coupled with the intermediate **7** affording the corresponding phenylethenylthiophenes **15–19** in satisfactory yields of ca. 60–90 % (Scheme 1C). Selective bromination with NBS furnished the bromothiophenes **20–24** (64–97 %), which underwent subsequent Heck olefination with vinylboronic acid pinacol ester **6** under optimized reaction conditions ([Pd<sub>2</sub>(dba)<sub>3</sub>], P(*t*Bu)<sub>3</sub>, DIPEA, toluene) to give boronic acid pinacol esters **25–29** [55–80 %; expect **27e** (33 %)]. These esters (branches) and tris(4-iodophenyl)amine **9** were finally threefold cross-coupled to furnish the target fluorophores **PM1–3** and **1–4** (55–70 %). Using 4-bromo-*N,N*-dimethylaniline **30** allowed the construction of the linear analogue **2aL**, whose X-ray analysis confirmed the exclusive *E*-configuration of both double bonds within the divinylthiophene linker (Figure S1).

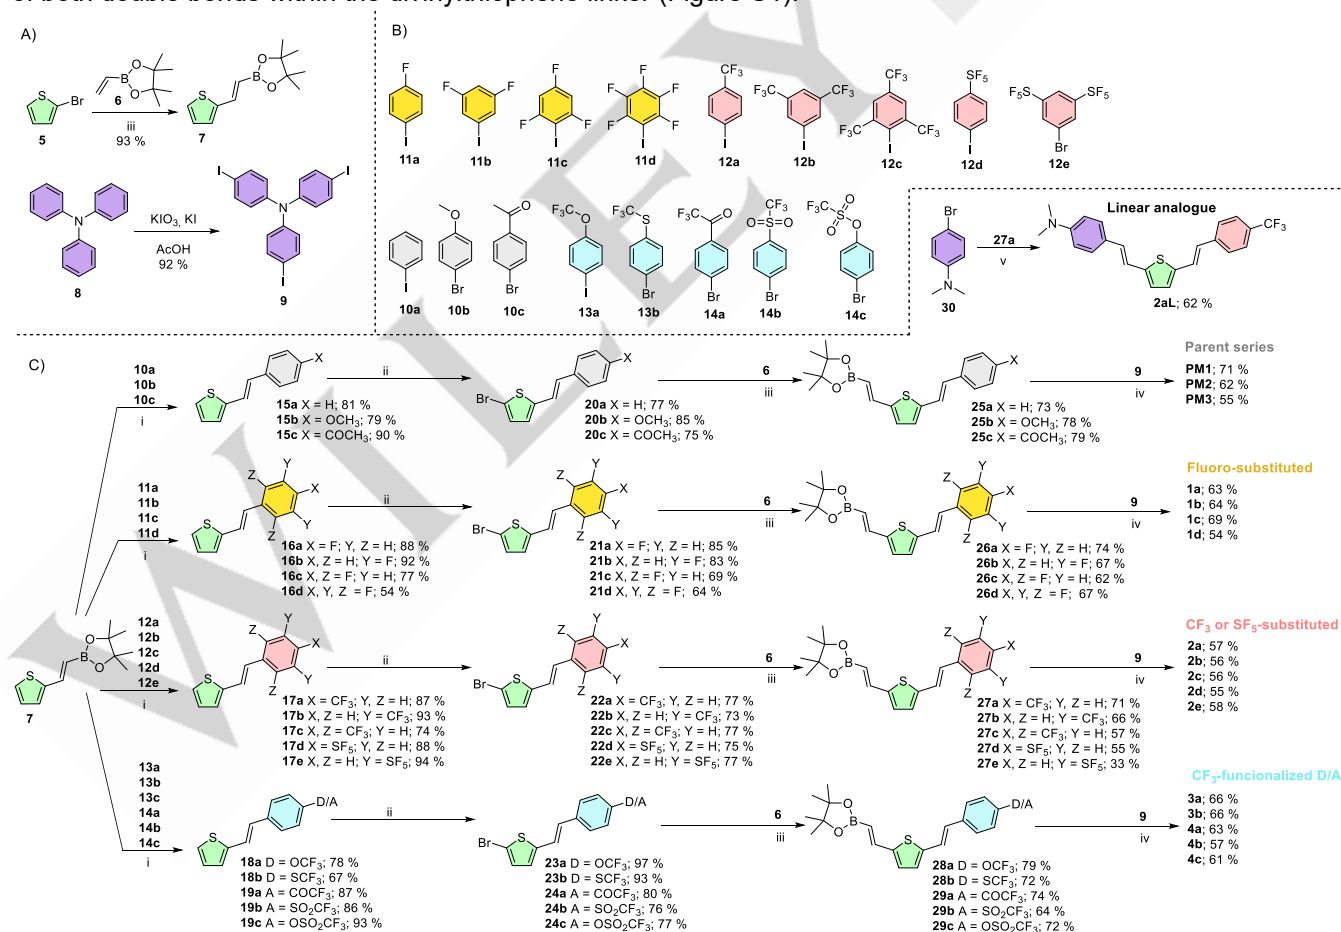

**Scheme 1.** Synthetic pathways towards tripodal fluorophores **1–4**. A) Synthesis of the key intermediates **7** and **9**. B) Structures of the starting bromo or iodobenzenes bearing fluoro acceptors. C) Straightforward four-step reaction pathway towards all target fluorophores **PM1–3** and **1–4**: i) **7** (1.1 eq), [PdCl<sub>2</sub>(PPh<sub>3</sub>)<sub>2</sub>] (0.02 eq), K<sub>2</sub>CO<sub>3</sub> (1.5 eq), THF/H<sub>2</sub>O 4:1, 60 °C, 18 h; ii) NBS (1.05 eq), CHCl<sub>3</sub>/AcOH 2:1, 80 °C, 18 h; iii) vinylboronic acid pinacol ester **6** (1.5 eq), [Pd<sub>2</sub>(dba)<sub>3</sub>] (0.01 eq), P(*t*Bu)<sub>3</sub> (0.05 eq), DIPEA (2 eq), toluene, 95 °C, 18 h; iv) corresponding boronic

## RESEARCH ARTICLE

acid pinacol ester (3.6 eq), [PdCl<sub>2</sub>(PPh<sub>3</sub>)<sub>2</sub>] (0.06 eq), K<sub>2</sub>CO<sub>3</sub> (5 eq), THF/H<sub>2</sub>O 4:1, 60 °C, 18 h; v) **27a** (1.1 eq), [PdCl<sub>2</sub>(PPh<sub>3</sub>)<sub>2</sub>] (0.02 eq), K<sub>2</sub>CO<sub>3</sub> (1.5 eq), THF/H<sub>2</sub>O 4:1, 60 °C, 2 h.

## Thermal Properties

Thermal properties of **PM1–3** and **1–4** were determined by differential scanning calorimetry, the recorded temperatures of melting  $T_m$ , glass transition  $T_g$  and thermal decomposition  $T_d$  are summarized in Table 1; the native DSC thermograms are provided in the SI. The studied compounds represent large tripodal structures with relatively high molecular weights (876–1632 g·mol<sup>-1</sup>), which hinder their crystallization and tend them to form amorphous glassy or semicrystalline solids upon precipitation from solution. Consequently, glass transitions of amorphous or broad melting processes of semicrystalline solids were primarily observed upon heating. A sharp endothermic melting, preceded by a cold crystallization at 137 °C, was recorded only for the pentafluorophenyl derivative **1d** at 223 °C. The semicrystalline compounds **PM2**, **1a**, **1c**, **2a**, **2b**, and **3a** underwent broad melting process (111–186 °C), but a reheating cycle was accompanied only by a glass transition, pointing to their complete amorphization. A distinctive and reversible glass transition ( $T_g$  = 89–147 °C) without any subsequent melting was observed for the remaining compounds. Whereas the tripodal **2a** showed only an exothermic irreversible peak at around 280 °C, the linear analogue **2aL** melted at 233 °C and exothermically decomposed up to 300 °C. The thermal degradation was generally recorded as either a vigorous or gradual exothermic process, with  $T_d$  values ranging from 210 to 420 °C. Sharing the same central TPA donor and the  $\pi$ -system, the differences in thermal behavior are attributed to the peripheral fluoro-acceptors. A rapid decomposition peak was revealed for **1d** (5×F), **2c** (3×CF<sub>3</sub>), **2d** (SF<sub>5</sub>), **3b** (SCF<sub>3</sub>), **4a** (COCF<sub>3</sub>), and **4c** (OSO<sub>2</sub>CF<sub>3</sub>), whereas a slow and gradual degradation was seen for molecules **PM1** (H), **PM2** (OCH<sub>3</sub>), **1a** (F), **2a** (CF<sub>3</sub>), **2b** (2×CF<sub>3</sub>), and **4b** (SO<sub>2</sub>CF<sub>3</sub>). Thermal stability is apparently enhanced by CF<sub>3</sub> groups in the series **2a–c** ( $T_d$  = 290–420 °C), by the two SF<sub>5</sub> groups in **2e** ( $T_d$  = 290 °C), and by the SO<sub>2</sub>CF<sub>3</sub> pendants in **4b** ( $T_d$  = 340 °C). Consequently, the highest thermal robustness was measured for **2c** ( $T_d$  = 420 °C) bearing nine peripheral trifluoromethyl groups.


**Table 1:** Thermal and electrochemical properties of fluorophores **PM1–3** and **1–4**.

	Comp.	$T_m$ [°C] <sup>[a]</sup>	$T_g$ [°C] <sup>[a]</sup>	$T_d$ [°C] <sup>[b]</sup>	$E_{1/2(ox1)}$ [V] <sup>[c]</sup>	$E_{p(ox2)}$ [V] <sup>[d]</sup>	$E_{1/2(red1)}$ [V] <sup>[c]</sup>	$\Delta E^{CV}$ [eV] <sup>[c]</sup>	$E_{HOMO}^{CV}$ [eV] <sup>[f]</sup>	$E_{LUMO}^{CV}$ [eV] <sup>[f]</sup>
Parent series	<b>PM1</b>	-	97	250	0.79	1.11	-1.81	2.60	-5.11	-2.51
	<b>PM2</b>	134	100	230	0.77	1.03	-1.89	2.66	-5.09	-2.43
	<b>PM3</b>	-	118	220	0.79	1.08	-1.62	2.41	-5.11	-2.70
Fluoro-subst.	<b>1a</b>	154	102	230	0.89	1.23	-1.73	2.62	-5.21	-2.59
	<b>1b</b>	-	92	240	0.88	1.14	-1.64	2.52	-5.20	-2.68
	<b>1c</b>	186	-	250	0.88	1.15	-1.69	2.57	-5.20	-2.63
	<b>1d</b>	223	114	250	0.88	1.15	-1.52	2.40	-5.20	-2.80
CF <sub>3</sub> - and SF <sub>5</sub> -subst.	<b>2a</b>	183	112	310	0.83	1.08	-1.68	2.51	-5.15	-2.64
	<b>2aL</b>	233	-	300	0.50	0.79	-1.97 <sup>[e]</sup>	2.47	-4.82	-2.35
	<b>2b</b>	120	107	290	0.81	1.08	-1.64	2.45	-5.13	-2.68
	<b>2c</b>	-	-	420	0.82	1.10	-1.42	2.24	-5.14	-2.90
	<b>2d</b>	-	135	230	0.82	1.09	-1.56 <sup>[e]</sup>	2.38	-5.14	-2.76
	<b>2e</b>	-	-	290	0.86	1.10	-1.45 <sup>[e]</sup>	2.31	-5.18	-2.87
CF <sub>3</sub> -functional. D/A	<b>3a</b>	111	89	220	0.75	1.08	-1.84	2.59	-5.07	-2.48
	<b>3b</b>	-	92	230	0.76	1.05	-1.72	2.48	-5.08	-2.60
	<b>4a</b>	-	110	210	0.86	1.12	-1.21	2.07	-5.18	-3.11
	<b>4b</b>	-	147	340	0.87	1.14	-1.30	2.17	-5.19	-3.02
	<b>4c</b>	-	100	230	0.85	1.13	-1.59 <sup>[e]</sup>	2.44	-5.17	-2.73

<sup>[a]</sup>  $T_m$  = temperature of melting,  $T_g$  = temperature of glass transition (the point of intersection of a baseline and a tangent of DSC peak/step = onset). <sup>[b]</sup>  $T_d$  = thermal decomposition (pyrolysis in N<sub>2</sub> atmosphere). <sup>[c]</sup>  $E_{1/2(ox1)}$  and  $E_{1/2(red1)}$  are half-wave potentials of the first oxidation and reduction, respectively, as measured by CV in THF containing 0.1 M Bu<sub>4</sub>NPF<sub>6</sub>; all potentials are given vs. SSCE,  $\Delta E^{CV} = E_{1/2(ox1)} - E_{1/2(red1)}$ . <sup>[d]</sup>  $E_{p(ox2)}$  is peak potential of the irreversible second (subsequent) oxidation. <sup>[e]</sup> Fully irreversible first reduction ( $E_p^c$  value). <sup>[f]</sup> Experimentally deduced  $E_{HOMO}^{CV}$  and  $E_{LUMO}^{CV}$ :  $-E_{HOMO}^{CV} = (E_{1/2(ox1)} + 0.036)$  or  $(E_{1/2(red1)} + 0.036) + 4.28$  (vs. SCE).<sup>[67,68]</sup> The increment of +0.036 V corresponds to the difference between SCE (0.241 vs. SHE) and SSCE (0.205 vs. SHE).<sup>[69]</sup>

## Electrochemistry

The electrochemical behavior of the target fluorophores **PM1–3** and **1–4** was investigated in THF containing 0.1 M Bu<sub>4</sub>NPF<sub>6</sub> using a three-electrode cell by cyclic voltammetry (CV). The acquired electrochemical data are summarized in Table 1, while further experimental details, recorded CV diagrams, and comparison of the tripodal and linear analogues are given in the SI.

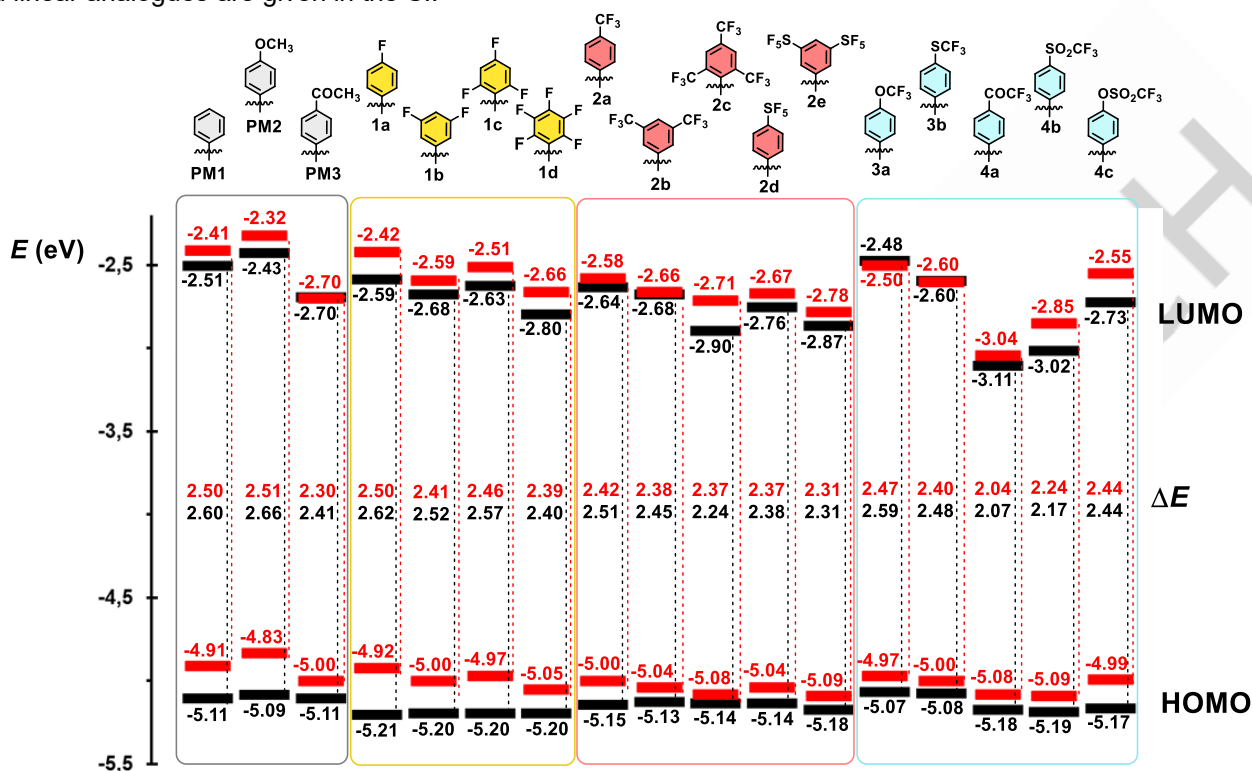

**Figure 2.** Energy level diagram of the electrochemically estimated (black) and the DFT-calculated (red) HOMO/LUMO values for fluorophores **PM1–3** and **1–4**.

Oxidation was recorded as a multi-electron process consisting of the first reversible one-electron oxidation appearing as a distinguishable shoulder ( $E_{1/2(\text{ox}1)}$ ), presumably involving the TPA donor, followed by consecutive irreversible oxidations ( $E_{\text{p}(\text{ox}2)}$ ) associated with the thiophene auxiliary donors. This electrochemical behavior is consistent with the TPA-( $\pi$ -Th- $\pi$ -FluoroA)<sub>3</sub> arrangement of the studied tripodal systems. Reduction is a multi-electron process occurring over the peripheral withdrawing groups as well as the adjacent  $\pi$ -system. The (quasi)reversible first reduction ( $E_{1/2(\text{red}1)}$ ) was recorded either as a shoulder or as a fully developed peak. However, the SF<sub>5</sub>- and F<sub>3</sub>CSO<sub>2</sub>O-substituted compounds **2d–e** and **4c** exhibited fully irreversible first reductions ( $E_{\text{p}(\text{red}1)}$ ), consistent with our previous observation.<sup>[50]</sup> The multi-electron transfer is related to the tripodal character and the number of appended fluorine atoms. For instance, incorporating two SF<sub>5</sub> (**2e**) or three CF<sub>3</sub> groups (**2c**) into each branch proportionally increases the number of transferred electrons during the consecutive reductions. The obtained half-wave potentials of the first oxidation and reduction  $E_{1/2(\text{ox}1/\text{red}1)}$  for tripodal **PM1–3** and **1–4** were found within the range of 0.75 to 0.89 V and –1.21 to –1.89 V, respectively, and were further converted into energy range (eV) in order to experimentally estimate the HOMO/LUMO levels (Table 1). The energy level diagram in Figure 2 visualizes the experimentally estimated HOMO/LUMO energies and electrochemical gaps  $\Delta E^{\text{CV}}$ . Taking the unsubstituted derivative **PM1** as the parent molecule ( $E_{\text{HOMO/LUMO}}^{\text{CV}} = -5.11/-2.51$  eV,  $\Delta E^{\text{CV}} = 2.60$  eV), the HOMO level remains relatively steady across the series and principal changes are seen in the LUMO level upon further substitution. The LUMO is raised/lowered depending on whether an electron donor or acceptor is appended, e.g. **PM2** with a methoxy donor ( $E_{\text{LUMO}}^{\text{CV}} = -2.43$  eV) or **PM3** bearing an electron-withdrawing acetyl group ( $E_{\text{LUMO}}^{\text{CV}} = -2.70$  eV). Attaching a single fluorine (**1a**), CF<sub>3</sub> (**2a**) or SF<sub>5</sub> (**1d**) into the *para* position gradually decreases the  $E_{\text{LUMO}}^{\text{CV}}$  from –2.59 to –2.76 eV as a result of increasing negative inductive effect and eventually employing negative hyperconjugation.<sup>[70]</sup> Beginning with these mono-substituted derivatives and gradually attaching additional fluorine-containing substituents (**1a**→**1d**, **2a**→**2c** or **2d**→**2e**), the LUMO is further deepened, with the narrowest

## RESEARCH ARTICLE

HOMO–LUMO gap observed for tris(trifluoromethyl) derivative **2c**. Nearly identical HOMO/LUMO levels were measured for the methoxy- and trifluoromethoxy-substituted molecules **PM2** and **3a**, indicating persistent mesomeric electron-donating behavior of both substituents. In contrast, a replacement of the chalcogens (O→S, **3a**→**3b**) lowers the LUMO energy due to the weaker donating ability of the SCF<sub>3</sub> group. Comparison of the acetyl and trifluoroacetyl derivatives **PM3** and **4a** reveals significantly pronounced electron-withdrawing character of the latter. Hence, compound **4a**, bearing three peripheral COCF<sub>3</sub> acceptors, possesses the narrowest HOMO–LUMO gap ( $\Delta E^{\text{CV}} = 2.07$  eV), whereas the analogous sulfone **4b** was found to be a less effective mesomeric acceptor ( $\Delta E_{\text{LUMO}}^{\text{CV}} \sim 0.1$  eV). Contradictorily to **PM2** and **3a**, the trifluoromethyl sulfonate group in **4c** behaves rather as an electron-acceptor and demonstrates electronic effects comparable to the SF<sub>5</sub>-group in **2d**. These trends, particularly for the *para*-substituted derivatives, correspond to the Hammett  $\sigma_p^-$  constants<sup>[41]</sup> as demonstrated by the correlation present in Figure S24, and identify the –SF<sub>5</sub>, –SO<sub>2</sub>CF<sub>3</sub>, and –COCF<sub>3</sub> groups as among the most powerful electron-withdrawing substituents within this series.

**Table 2:** Linear and nonlinear optical data of fluorophores **PM1–3** and **1–4** in THF.

Comp.	Solution							Powder	
	$\lambda_{\text{max}}^{\text{A}}$ [nm/eV] <sup>[a]</sup>	$\epsilon_{\text{max}}^{\text{A}}$ [10 <sup>3</sup> M <sup>-1</sup> cm <sup>-1</sup> ] <sup>[a]</sup>	$\lambda_{\text{max}}^{\text{E}}$ [nm/eV] <sup>[a]</sup>	$\langle \tau \rangle$ [ns] <sup>[a]</sup>	$\phi^{\text{F}}$ [-] <sup>[b]</sup>	Stokes shift [cm <sup>-1</sup> /eV]	$\delta_{2\text{PA}}/\lambda_{2\text{PA}}$ [GM/nm] <sup>[c]</sup>	$\lambda_{\text{max}}^{\text{E}}$ [nm] <sup>[d]</sup>	
Parent series	<b>PM1</b>	443/2.80	181	535/2.32	1.61	0.50	3880/0.48	890/740	[f]
	<b>PM2</b>	443/2.80	159	521/2.38	1.39	0.56	3380/0.42	850/740	[f]
	<b>PM3</b>	456/2.72	110	585/2.12	1.90	0.47	4840/0.60	550/730	650
Fluoro-subst.	<b>1a</b>	442/2.81	134	535/2.32	1.65	0.46	3900/0.49	910/740	[f]
	<b>1b</b>	448/2.77	117	562/2.21	1.93	0.49	4530/0.56	800/740	[f]
	<b>1c</b>	446/2.78	105	550/2.25	1.92	0.54	4240/0.53	610/740	[f]
	<b>1d</b>	457/2.71	146	587/2.11	2.23	0.52	4850/0.60	810/740	[f]
CF <sub>3</sub> - and SF <sub>5</sub> -subst.	<b>2a</b>	450/2.76	130	563/2.20	1.91	0.49	4460/0.55	670/740	[f]
	<b>2aL</b>	429/2.89	55.6	583/2.13	[h]	[h]	6160/0.76	[h]	[f]
	<b>2b</b>	453/2.74	119	583/2.13	2.06	0.48	4920/0.61	560/740	[f]
	<b>2c</b>	443/2.80	175	[e]	0.32	[e]	[e]	[g]	622
	<b>2d</b>	452/2.74	138	578/2.15	1.94	0.45	4820/0.60	530/740	[f]
	<b>2e</b>	458/2.71	120	603/2.06	1.90	0.36	5250/0.65	1930/740	617
CF <sub>3</sub> -function. D/A	<b>3a</b>	444/2.79	129	545/2.28	1.76	0.48	4170/0.52	1250/740	[f]
	<b>3b</b>	452/2.74	118	568/2.18	1.87	0.49	4520/0.56	780/750	[f]
	<b>4a</b>	478/2.59	163	678/1.83	0.34	0.06	6170/0.77	[g]	[f]
	<b>4b</b>	473/2.62	124	665/1.86	0.64	0.11	6100/0.76	1170/730	710
	<b>4c</b>	447/2.77	134	553/2.24	1.83	0.49	4290/0.53	710/740	[f]


<sup>[a]</sup> Measured in THF (Dimroth-Reichardt polarity parameter  $E_T^N = 0.207$ <sup>[71]</sup>) at concentration  $\approx 5 \times 10^{-6}$  M; emitted at the absorption maximum wavelength. <sup>[b]</sup> Fluorescence quantum yield ( $\pm 10\%$ ) determined relative to perylene as a standard ( $\phi^{\text{F}} = 0.94$  in cyclohexane).<sup>[72]</sup> <sup>[c]</sup> Measured in THF. <sup>[d]</sup> Emitted at the absorption maximum wavelength determined in THF solution. <sup>[e]</sup> Non-emissive in THF. <sup>[f]</sup> Low intensity of emission in solid state. <sup>[g]</sup> Low 2PA excitation fluorescence signal. <sup>[h]</sup> Not measured.

### Linear Optical Properties


Chromophores **PM1–3** and **1–4** are intensively orange or red solids, with their fundamental photophysical parameters listed in Tables 2 (THF), S2 (toluene), and S3 (acetonitrile). The absorption and emission spectra of representative **PM1**, **1a**, **2a**, and **2d** in THF are shown in Figure 2. Based on the Frenkel exciton model,<sup>[8]</sup> three excited states are generally predicted for C<sub>3</sub>-symmetric tripodal chromophores. However, the two low-energy states (relative to the corresponding linear chromophore) are expected to be degenerate, while the high-energy state possesses zero oscillator strength. Consequently, the absorption spectra of tripodal chromophores typically appear as a single band corresponding to that of the linear analogue.<sup>[50,73]</sup> Fluorophores **PM1–3** and **1–4** exhibit a single absorption band (Figures S25–29), accompanied by a high-energy shoulder at around 360 nm. When comparing the linear **2aL** ( $\lambda_{\text{max}}^{\text{A/E}} = 429/583$  nm) with the tripodal **2a** ( $\lambda_{\text{max}}^{\text{A/E}} = 450/563$  nm), both absorption and emission spectra are nearly identical (Figure S30), supporting the aforementioned assumption. The longest-wavelength absorption maxima of the tripodal fluorophores **PM1–3** and **1–4** lie between 442 and 478 nm, with molar absorption

## RESEARCH ARTICLE

coefficients in the range of  $105\text{--}180 \times 10^3 \text{ M}^{-1}\text{cm}^{-1}$ . This contrasts with the linear derivative **2aL** ( $\epsilon_{\text{max}} = 55.6 \times 10^3 \text{ M}^{-1}\text{cm}^{-1}$ ). Thus, increasing the number of chromophoric units enhances the absorption, which is a typical feature of linear vs. tripod systems.<sup>[73]</sup> In agreement with the electrochemical measurements, the observed red/blue shifts in the absorption maxima arise from structural variations in the fluorine-based peripheral substituents. The same trends are obeyed as can be demonstrated by a tight correlation of the optical ( $1240/\lambda_{\text{max}}^{\text{A}}$ ) and electrochemical gaps ( $\Delta E$ ), see Figures S35 in the SI. Fluorophore **2c** features different photophysical behavior, including blue-shifted absorption maxima, substantially quenched fluorescence in THF, the most red-shifted emission band in toluene, and intense solid-state emission. This behavior is likely associated with a nonplanar arrangement of the terminal phenyl ring caused by *ortho*-substitution with bulky  $\text{CF}_3$ -groups.<sup>[74]</sup> The most red-shifted CT bands were recorded for **4a** and **4b** (478 and 473 nm), bearing  $-\text{COCF}_3$  and  $-\text{SO}_2\text{CF}_3$  powerful acceptors. Only minor solvatochromism was detected in the absorption spectra (Figure S31–34), which is a typical feature of push–pull chromophores.<sup>[75]</sup>

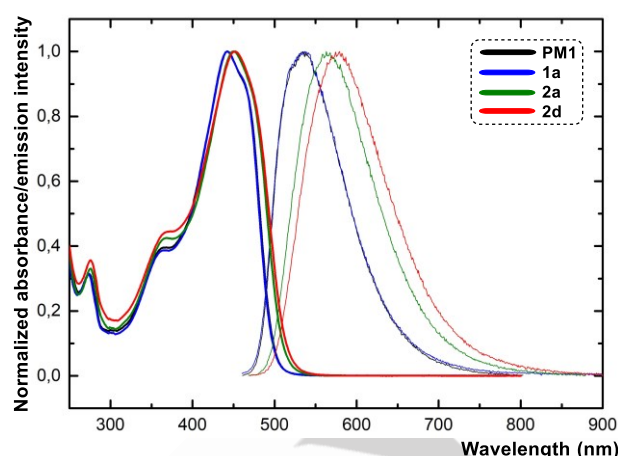

**Figure 3.** Normalized UV-Vis absorption (bold line) and emission spectra (thin line) of fluorophores **PM1** (4-H), **1a** (4-F), **2a** (4- $\text{CF}_3$ ), and **2d** (4- $\text{SF}_5$ ) measured in THF ( $c \approx 5 \times 10^{-6} \text{ M}$ ).

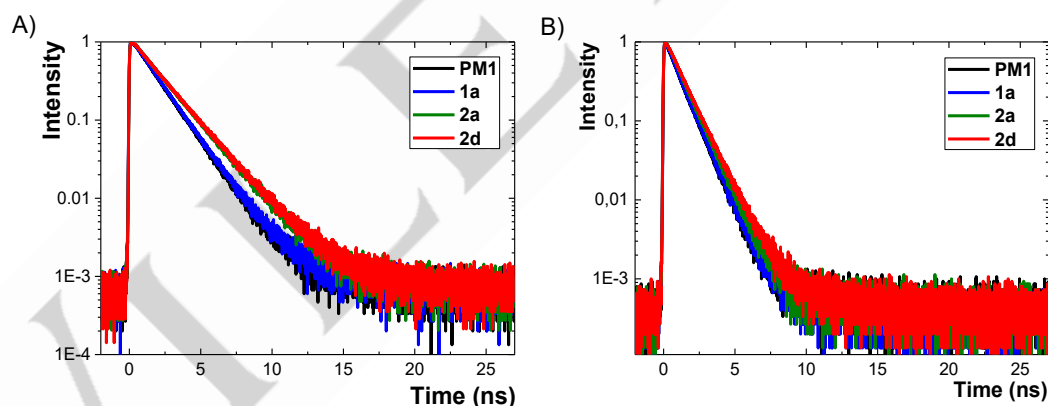

**Figure 4.** Fluorescence decays in the ns timescale for fluorophores **PM1** (4-H), **1a** (4-F), **2a** (4- $\text{CF}_3$ ), and **2d** (4- $\text{SF}_5$ ) measured in A) THF and B) toluene ( $c \approx 5 \times 10^{-6} \text{ M}$ ).

The target molecules showed a single broad emission band in THF and ACN, while an apparent low-energy shoulder was recorded in nonpolar toluene due to vibronic transitions commonly found in nonpolar media.<sup>[76]</sup> Compared to the absorption spectra, the emission maxima of **PM1–3** and **1–4** span a broad range (521 to 678 nm) and are obviously much more influenced by the structural aspects, similarly to the aforementioned electrochemical data (see Figure S36 for the correlation). This implies a greater polarization/stabilization of the excited state, arising from considerable structural/geometrical reorganization compared to the ground state. As expected, this effect is most pronounced for the nonplanar **2c**, which showed the largest Stokes shift above  $6100 \text{ cm}^{-1}$  in toluene (Table S2). In general, the emission maximum shifts bathochromically with an increasing number of fluorine atoms/fluorine-based substituents or upon replacing  $\text{CH}_3$  by  $\text{CF}_3$  groups. A positive solvatochromism observed in more polar solvents (ACN) further confirms the polar nature of the excited state, however, the stabilization is accompanied by a diminished fluorescence intensity. In THF, the fluorescence quantum yields ( $\Phi^{\text{F}}$ ) range within a narrow interval of 0.36–0.56 and decrease significantly upon attaching powerful withdrawing substituents ( $-\text{COCF}_3$  and  $-\text{SO}_2\text{CF}_3$ ), which enhance ICT, as in **4a–b** ( $\Phi^{\text{F}} = 0.06\text{--}0.11$ ). A similarly narrow range of  $\Phi^{\text{F}}$  values (0.44–0.54)

## RESEARCH ARTICLE

was found in toluene. The excited states of **PM1–3** and **1–4** were further studied by fluorescence-decay measurements in toluene and THF (Figures 4 and S37–46 and Tables 2 and S4–S5). The average fluorescence lifetimes  $\tau$  range from 0.3 to 2.2 ns (THF, Table 2) and depend on both structural changes and solvent polarity. Figure 4 presents the decay profiles for the representative fluorophores **PM1**, **1a**, **2a**, and **2d** in toluene and THF showing extended lifetimes for chromophores with a larger number of fluorine atoms and fluorine-based substituents. On the contrary, replacing CH<sub>3</sub> by CF<sub>3</sub> in the acetyl group (**PM3**→**4a**) results in a substantial decrease in the lifetime (1.9→0.34 ns), while it increases again for **4b** (0.64 ns, –SO<sub>2</sub>CF<sub>3</sub>) and **4c** (1.83 ns, –OSO<sub>2</sub>CF<sub>3</sub>). However, **4a–c** exhibited even longer lifetimes in toluene than the parent systems **PM2/3** (Table S5).

Fluorophores **PM3**, **2c**, **2e**, and **4b**, all bearing powerful withdrawing termini, also showed a noticeable solid-state emission (Table 2, Figures S47–48). Compared to their solution emissions, the solid-state emission spectra are red-shifted and display low-energy shoulders, indicating significant intermolecular interactions and possible formation of excimers.<sup>[77]</sup> Fluorophore **2c** exhibits the strongest solid-state intensity, attributed to the *ortho*-oriented CF<sub>3</sub>-groups, which affect molecular packing in the solid state.<sup>[78]</sup> The nonplanar arrangement restricts an intramolecular rotation and opens aggregation-induced emission.<sup>[74]</sup>

## Theoretical DFT Calculations

The spatial, electronic and optical properties of the target fluorophores **PM1–3** and **1–4** were further predicted using DFT methods implemented in Gaussian@16W software package.<sup>[79]</sup> The initial geometries, frontier molecular orbital energies, and ground-state dipole moments  $\mu_g^{\text{DFT}}$  were optimized/calculated by the DFT B3LYP/6–311+G(2d,p) method in THF (Table 3). Theoretical electronic absorption spectra were calculated at the TD-DFT (nstates = 8) level using both B3LYP/6–311++G(2d,p) and CAM-B3LYP/6–311++G(2d,p) functionals in THF, and the corresponding  $\lambda_{\text{max}}^{\text{DFT}}$  values were extracted for both methods, see the SI for more details. The optimized geometry of the representative fluorophore **1d** (Figure 5A) reveals completely planar branches appended to the propeller-shaped TPA, this structural feature is consistent across other molecules in the series. However, it contrasts with the twisted terminal phenyls (dihedral angle ~ 50 °) of **2c** bearing the bulky trifluoromethyl groups. This geometrical distinction further supports our aforementioned conclusions drawn from the experimental photophysical data. For a comparison between the tripodal and linear analogues **2a/2aL**, see the SI.

**Table 3:** The DFT calculated data of fluorophores **PM1–3** and **1–4**.

Comp.	$E_{\text{HOMO}}^{\text{DFT}}$ [eV] <sup>[a]</sup>	$E_{\text{HOMO}-1(-2)}^{\text{DFT}}$ [eV] <sup>[a]</sup>	$E_{\text{LUMO}(+1)}^{\text{DFT}}$ [eV] <sup>[a]</sup>	$E_{\text{LUMO}+2}^{\text{DFT}}$ [eV] <sup>[a]</sup>	$\Delta E^{\text{DFT}}$ [eV] <sup>[a]</sup>	$\mu_g^{\text{DFT}}$ (D) <sup>a</sup>	$\lambda_{\text{max}}^{\text{DFT}}$ (nm/eV) <sup>[b]</sup>	$\lambda_{\text{max}}^{\text{DFT}}$ (nm/eV) <sup>[c]</sup>	
Parent series	<b>PM1</b>	–4.91	–5.40	–2.41	–2.20	2.50	1.4	577/2.15	451/2.75
	<b>PM2</b>	–4.83	–5.24	–2.32	–2.10	2.51	2.6	575/2.16	454/2.73
	<b>PM3</b>	–5.00	–5.53	–2.70	–2.57	2.30	0.8	623/1.99	467/2.66
Fluoro-subst.	<b>1a</b>	–4.92	–5.41	–2.42	–2.22	2.50	3.4	576/2.15	462/2.68
	<b>1b</b>	–5.00	–5.54	–2.59	–2.40	2.41	4.6	550/2.25	430/2.88
	<b>1c</b>	–4.97	–5.50	–2.51	–2.32	2.46	2.6	572/2.17	446/2.78
	<b>1d</b>	–5.05	–5.62	–2.66	–2.49	2.39	5.6	583/2.13	446/2.78
CF <sub>3</sub> - and SF <sub>5</sub> -subst.	<b>2a</b>	–5.00	–5.54	–2.58	–2.41	2.42	9.4	598/2.07	459/2.70
	<b>2aL</b>	–4.98	–5.96(–7.01)	–2.38(–1.25)	–0.84	2.60	10.9	534/2.32	448.2.77
	<b>2b</b>	–5.04	–5.61	–2.66	–2.50	2.38	9.0	593/2.09	451/2.75
	<b>2c</b>	–5.08	–5.72	–2.71	–2.58	2.37	4.6	608/2.04	– <sup>[d]</sup>
	<b>2d</b>	–5.04	–5.60	–2.67	–2.51	2.37	9.2	600/2.07	453/2.74
	<b>2e</b>	–5.09	–5.69	–2.78	–2.64	2.31	10.5	623/1.99	465/2.67
CF <sub>3</sub> -functional. D/A	<b>3a</b>	–4.97	–5.49	–2.50	–2.31	2.47	3.5	587/2.11	455/2.73
	<b>3b</b>	–5.00	–5.54	–2.60	–2.44	2.40	8.6	596/2.08	456/2.72
	<b>4a</b>	–5.08	–5.63	–3.04	–2.96	2.04	10.5	698/1.78	488/2.54
	<b>4b</b>	–5.09	–5.67	–2.85	–2.73	2.24	13.3	621/2.00	456/2.72
	<b>4c</b>	–4.99	–5.51	–2.55	–2.36	2.44	3.8	572/2.17	441/2.81

<sup>[a]</sup> Calculated using the DFT B3LYP/6–311+G(2d,p) level in THF. <sup>[b]</sup> Calculated using the TD-DFT (nstates = 8) B3LYP/6–311++G(2d,p) level in THF. <sup>[c]</sup> Calculated using the TD-DFT (nstates = 8) CAM-B3LYP/6–311++G(2d,p) level in THF.


<sup>[d]</sup> Calculation failed.

## RESEARCH ARTICLE

The calculated HOMO and LUMO energies  $E_{\text{HOMO/LUMO}}^{\text{DFT}}$  (Figure 2) follow the same trends as seen by the CV measurements, and the calculated  $E_{\text{LUMO}}^{\text{DFT}}$  and HOMO–LUMO gaps correlate tightly with the experimental values (Figures S50–S51). As a general trend, the steady HOMO and the varied LUMO were observed upon changing the terminal fluorine-based substituents. Nearly identical energies were calculated for the HOMO–1/–2 and the LUMO/+1, indicating these pairs of FMOs to be degenerate (Figure 5B), which is in accordance with previous observations.<sup>[50,80]</sup>

Visualization of the FMOs in the representative chromophore **2a** (Figure 5B; see also Figures S52–S60 for other derivatives) shows that the HOMO is localized on the central TPA unit, while the HOMO–1 is spread over the auxiliary thiophene donor and the adjacent  $\pi$ -system of one branch. The degenerate HOMO–2 displays an analogous distribution over the remaining two branches. The unoccupied orbitals display heterogenous distributions depending on the electron-withdrawing strength of the given acceptor. Fluorophores with weak or absent acceptors possess the LUMO+2 spread over both the thiophene and the adjacent  $\pi$ -system across all three branches (except **2c**). Increasing acceptor character shifts LUMO+2 toward the terminal phenyls (**2b–e**) or directly onto the mesomeric acceptors (**PM3, 4a–b**). The LUMO+1 is transitioned from the central TPA donor (**PM2, 1a, 2a, and 3b**) to individual arm (**PM1, 1b–c, 2d–e, and 3a or 1d, 2b, 2c, and 4c**) and finally to the terminal strong acceptors (**PM3, 4a, 4b**), depending on withdrawing strength. The LUMO itself exhibits a nearly identical distribution as the degenerate LUMO+1 across the second (or third) branch(es), a such splitting is a typical feature of tripodal D( $-\pi$ -A)<sub>3</sub> scaffolds.<sup>[61]</sup> Hence, the degree of charge separation in the studied molecules can be effectively tuned by varying the electron-withdrawing ability of the terminal substituents.


The UV-Vis absorption spectra of target fluorophores **PM1–3** and **1–4** were predicted using two different functionals, namely B3LYP and CAM-B3LYP in THF (Table 3 and Figures S61–S68). While the CAM-B3LYP-calculated spectra align well with the experimental bands, the B3LYP-derived spectra obey the shape of the experimental ones but are shifted bathochromically. However, when correlating the experimental and theoretical  $\lambda_{\text{max}}$  values, the CAM-B3LYP-derived longest-wavelength absorption maxima showed no meaningful correlation, whereas the B3LYP-calculated data fit well with the experimental values (Figure S69), including the high-energy shoulder. Transition analysis (Figure 5B) revealed that the longest-wavelength band (534–698 nm) originates from two principal transitions: HOMO  $\rightarrow$  LUMO or HOMO  $\rightarrow$  degenerate LUMO+1, both exhibiting the same oscillator strength. The high-energy band arises from four transitions between the degenerate HOMO–1/HOMO–2 to the degenerate LUMO/LUMO+1. All these transitions possess the same oscillator strengths (roughly half those responsible for the CT-band), correspond well to the experimental data, and are largely neglected by the CAM-B3LYP functional. Altogether, the DFT predicted outcomes are in line with the TPA-( $\pi$ -Th- $\pi$ -FluoroA)<sub>3</sub> structural arrangement, exhibiting two principal ICTs originating from both the TPA and thiophene donors (Figure 5B).

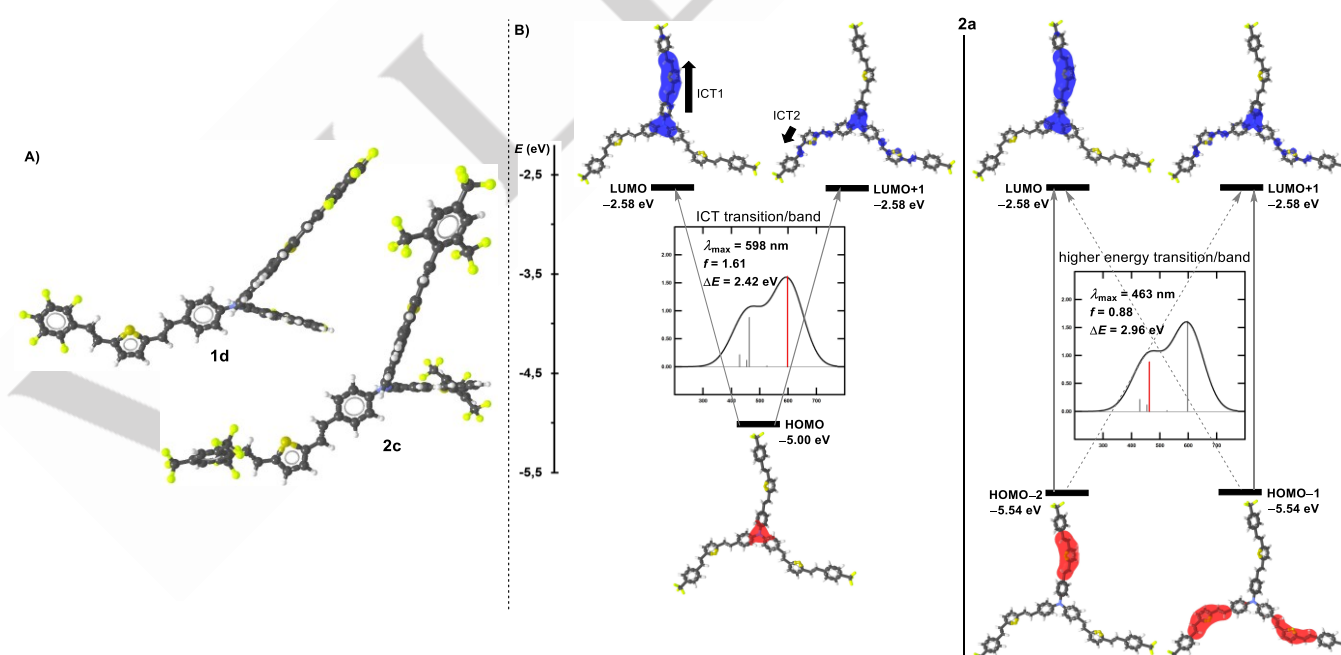

**Figure 5.** A) Optimized geometries of fluorophores **1d** and **2c** calculated using DFT B3LYP/6-311+G(2d,p) level; color of atoms: carbon – black, hydrogen – white, nitrogen – blue, sulfur – yellow, fluorine – yellow-green. B) The principal electron transitions, FMOs and DFT-calculated parameters of the representative trifluoromethyl derivative **2a** [the HOMO(–1,–2) are shown in red, the LUMO(+1,+2) in blue; the vertical lines in the calculated absorption spectra represent oscillator strengths ( $f$ )].

## Two-Photon Absorption Properties

With respect to their adjustable ICT character and tripodal arrangement, the two-photon absorption properties of **PM1–3** and **1–4** were further examined by a two-photon excited fluorescence (TPEF) method in THF and toluene (Tables 2 and S2 and Figures 6 and S70–S79). Except **2c** and **4a**, the investigated fluorophores generally exhibited good to excellent 2PA performance, with 2PA cross sections around 1000 GM. When going from the unsubstituted derivative **PM1** to the monofluoro-substituted derivative **1a**, the peak 2PA cross-section at 740 nm in THF slightly increases from 890 to 910 GM; however, the effect is far more pronounced in toluene (1380 GM at 750 nm). Further addition of the fluorine atoms (**1a**→**1d**) did not improve the 2PA activity. Attaching the trifluoromethyl along with the *para*-pentafluorosulfanyl substituents proved rather detrimental, whereas the introduction of two *meta*-positioned SF<sub>5</sub> groups together with the polarizable branches in **2e** yields an exceptional 2PA cross-section of 1930 GM in THF (Table 2). When comparing **2e** to structurally related chromophores, bearing olefinic<sup>[49]</sup> and acetylenic units<sup>[50]</sup> and possessing markedly different cross-sections of around 2000 and 500 GM, the influence of a planar chromophoric unit and a cumulation effect of two SF<sub>5</sub> groups must be highlighted. Further increasing the ICT by employing strong mesomeric acceptors such as COCF<sub>3</sub> (**4a**) results in a dramatic drop of the TPEF signal, falling below a detectable limit, whereas the trifluoromethyl sulfone derivative **4b** still displayed a noticeable cross-section of 1170 GM. Interestingly, derivative **3a**, bearing three pseudo-donating OCF<sub>3</sub> groups, exhibited an enhanced  $\delta_{2PA}$  of 1250 GM, surpassing the 850 GM observed for its methoxy-substituted analogue **PM2**. This further demonstrates that balancing the D/A behavior of the OCF<sub>3</sub> group through a combination of –I and +M effects may represent a viable strategy for increasing two-photon activity. Our TPEF measurements clearly show that a pronounced ICT tends to suppress the two-photon absorption cross-section, particularly in non-polar solvents where stabilization of radiative ICT states is diminished. Chromophores with strong mesomeric acceptors (**PM3**, **4a**, **4b**) show the lowest 2PA cross-sections in toluene, whereas analogues containing none/moderate acceptors (**PM1–PM2**, **1a**, **2a**, **2d**, **3a–b**) maintain higher radiative efficiency, despite lacking octopolar features. Hence, the structural arrangement (D(– $\pi$ –A)<sub>3</sub> or D(– $\pi$ –D)<sub>3</sub>, planarization and composition of the chromophoric units, properly adjusting the extent of ICT, and selecting an appropriate environment seem to be proper tools to design organic absorbers with admirable 2PA activity. Considering the whole portfolio of studied fluorine-based peripheral moieties, the 3,5-diSF<sub>5</sub>-substituted chromophore **2e** stands out as particularly exceptional.

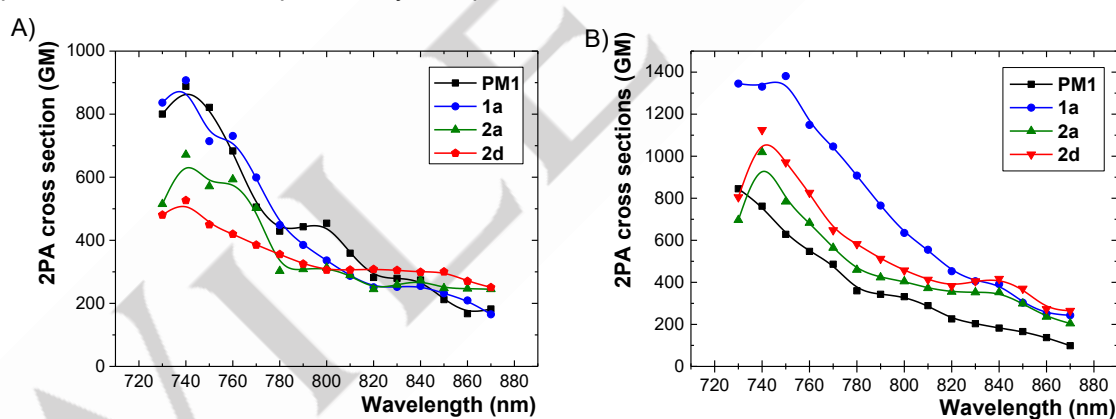

**Figure 6.** Two-photon absorption spectra for fluorophores **PM1** (4-H), **1a** (4-F), **2a** (4-CF<sub>3</sub>), and **2d** (4-SF<sub>5</sub>) measured in A) THF and B) toluene.

## Conclusion

Starting from the central TPA donor, we constructed a comprehensive series of propeller-shaped, C<sub>3</sub>-symmetric tripodal push–pull fluorophores by linking polarizable 2,5-divinylthiophene units with peripheral fluorinated phenyl rings acting as weak-to-strong electron acceptors. In addition to the tripodal push-pull chromophores **1–4**, the series was complemented by one linear (**2aL**) and three non-fluorinated parent compounds (**PM1–3**), allowing a thorough comparison across the entire library. The systematic structural variation allowed controlled modulation of the intramolecular charge-transfer (ICT) character, providing a platform to evaluate how subtle changes in the degree of fluorination affect the linear and nonlinear photophysical properties. The target fluorophores were obtained as orange-to-red amorphous or semicrystalline solids with high solubility in solvents of medium and low polarity and with distinct glass transitions or melting processes, reflecting their amorphous or semicrystalline nature. Thermal stability was generally high, with the –CF<sub>3</sub> and –SO<sub>2</sub>CF<sub>3</sub>-functionalized derivatives **2a–c** and **4b** displaying the greatest robustness. In general, peripheral F-functionalization can greatly enhance

## RESEARCH ARTICLE

thermal stability. Electrochemical measurements revealed relatively steady HOMO localized at the central TPA unit, while the LUMO energies were strongly modulated by the electron-withdrawing strength of the peripheral substituents. According to the LUMO energies, the electron withdrawing power of the investigated (per)fluoro groups follows the order:  $\text{OCF}_3 \approx \text{H} < -\text{SCF}_3 \approx -\text{F} < -\text{CF}_3 < -\text{SF}_5 \approx -\text{OSO}_2\text{CF}_3 < -\text{SO}_2\text{CF}_3 < -\text{COCF}_3$ . Thus, the trifluoromethoxy group acts as an electronically neutral substituent, whereas the trifluoroacetyl proved to be a highly potent electron acceptor. The steady-state absorption spectra were largely insensitive to structural variations, whereas the emission properties exhibited a strong dependence on the extent of ICT and solvent polarity, with emission maxima tunable from 521 to 678 nm in THF and fluorescence lifetimes ranging from 0.3 to 2.2 ns. Hence, a radiative relaxation can be effectively controlled through the peripheral substitution. The twisted arrangement of the *ortho*-oriented  $\text{CF}_3$  groups in **2c** imparts different photophysics in solution and enhanced solid-state fluorescence, further illustrating the critical role of substituent orientation. The experimentally measured two-photon absorption cross-sections ranged from 500 to 1300 GM in THF and toluene, while fluorophore **2e**, bearing two meta-positioned  $-\text{SF}_5$  groups, demonstrated an exceptional 2PA cross-section of 1930 GM. In contrast, the two-photon activity of the trifluoroacetyl derivative **4a** was nearly zero in THF. Thus, taking the steady central donor and the conjugated system, the peripheral F-substitution can either boost or quench the NLO activity through controlling the extent of ICT. These results demonstrate that the interplay between the polarizability of the particular chromophoric units, the substituent electronic nature, and the molecular symmetry is crucial for enabling efficient two-photon transitions. This study establishes general principles showing that a careful selection and positioning of the F-substituents can finely modulate ICT and tailor both linear and nonlinear photophysical properties of TPA-centered tripodal fluorophores with perspective applications across 2PA bioimaging, optical data storage, and other nonlinear photonic technologies, where a precise control over the ICT and the two-photon response is essential.

## Supporting Information

The authors have cited additional references within the Supporting Information.<sup>[81–97]</sup> The data supporting this article have been included as part of the SI, and the dataset available at <https://doi.org/10.6084/m9.figshare.30646283>. Crystallographic data for **2aL** has been deposited at the [CCDC] under [2502796] and can be obtained from [<https://www.ccdc.cam.ac.uk>].

## Acknowledgements

This work has been funded by a grant from the Programme Johannes Amos Comenius under the Ministry of Education, Youth and Sports of the Czech Republic [No. CZ.02.01.01/00/23\_021/0008593].

**Keywords:**  $\text{C}_3$ -symmetric fluorophores • two-photon absorption (2PA) • fluorination effect • intramolecular charge transfer (ICT) • DFT calculations

## References

- [1] P. Blanchard, C. Malacrida, C. Cabanetos, J. Roncali, S. Ludwigs, "Triphenylamine and Some of Its Derivatives as Versatile Building Blocks for Organic Electronic Applications" *Polym. Int.* **2019**, *68*, 589.
- [2] X. Lian, Z. Zhao, D. Cheng, "Recent Progress on Triphenylamine Materials: Synthesis, Properties, and Applications" *Mol. Cryst. Liq. Cryst.* **2017**, *648*, 223.
- [3] L. H. Hao, E. D. Dai, Y. Q. Ban, Q. Y. Zhang, M. R. Wang, P. Wang, Q. L. Zhao, Y. J. Zhao, X. Wang, L. H. Teng, "Strong Nonlinear Optical Response in Star-Shaped Push–Pull Triphenylamine Derivatives" *Indian J. Phys.* **2025**, *99*, 2627.
- [4] M. Klikar, P. Solanke, J. Tydlitát, F. Bureš, "Alphabet-Inspired Design of (Hetero)Aromatic Push–Pull Chromophores" *Chem. Rec.* **2016**, *16*, 1886.
- [5] D. Beljonne, W. Wenseleers, E. Zojer, Z. Shuai, H. Vogel, S. J. K. Pond, J. W. Perry, S. R. Marder, J.-L. Brédas, "Role of Dimensionality on the Two-Photon Absorption Response of Conjugated Molecules: The Case of Octupolar Compounds" *Adv. Funct. Mater.* **2002**, *12*, 631.
- [6] X. Wang, P. Yang, G. Xu, W. Jiang, T. Yang, "Two-Photon Absorption and Two-Photon Excited Fluorescence of Triphenylamine-Based Multibranching Chromophores" *Synth. Met.* **2005**, *155*, 464.
- [7] Y. Gong, G. L. Hou, X. Bi, M. Hu, N. Kuthirummal, A. A. Teklu, J. Koenemann, N. Harris, P. Wei, K. Devera, M. Hu "Enhanced Two-Photon Absorption in Two Triphenylamine-Based All-Organic Compounds" *J. Phys. Chem. A* **2021**, *125*, 1870.

## RESEARCH ARTICLE

- [8] C. Katan, F. Terenziani, O. Mongin, M. H. V. Werts, L. Porrès, T. Pons, J. Mertz, S. Tretiak, M. Blanchard-Desce, "Effects of (Multi)Branching of Dipolar Chromophores on Photophysical Properties and Two-Photon Absorption" *J. Phys. Chem. A* **2005**, *109*, 3024.
- [9] H. M. Kim, B. R. Cho, "Two-Photon Materials with Large Two-Photon Cross Sections. Structure-Property Relationship" *Chem. Commun.* **2009**, 153.
- [10] T. C. Lin, S. J. Chung, K. S. Kim, X. Wang, G. S. He, J. Swiatkiewicz, H. E. Pudavar, P. N. Prasad in *Polymers for Photonics Applications II* (Ed.: K. S. Lee), Springer Berlin Heidelberg, Berlin, Heidelberg, **2003**, pp. 157–193.
- [11] M. Pawlicki, H. A. Collins, R. G. Denning, H. L. Anderson, "Two-Photon Absorption and the Design of Two-Photon Dyes" *Angew. Chem. Int. Ed.* **2009**, *48*, 3244.
- [12] F. Terenziani, C. Katan, E. Badaeva, S. Tretiak, M. Blanchard-Desce, "Enhanced Two-Photon Absorption of Organic Chromophores: Theoretical and Experimental Assessments" *Adv. Mater.* **2008**, *20*, 4641.
- [13] I. Kammerer, J. Nemirovsky, M. Segev, "Optimizing 3D Multiphoton Fluorescence Microscopy" *Opt. Lett.* **2013**, *38*, 3945.
- [14] S. Yao, K. D. Belfield, "Two-Photon Fluorescent Probes for Bioimaging" *Eur. J. Org. Chem.* **2012**, 3199.
- [15] H. M. Kim, B. R. Cho, "Small-Molecule Two-Photon Probes for Bioimaging Applications" *Chem. Rev.* **2015**, *15*, 5014.
- [16] W. Niu, L. Guo, Y. Li, S. Shuang, C. Dong, M. S. Wong, "Highly Selective Two-Photon Fluorescent Probe for Ratiometric Sensing and Imaging Cysteine in Mitochondria" *Anal. Chem.* **2016**, *88*, 1908.
- [17] H. M. Kim, B. R. Cho, "Two-Photon Probes for Intracellular Free Metal Ions, Acidic Vesicles, and Lipid Rafts in Live Tissues" *Acc. Chem. Res.* **2009**, *42*, 863.
- [18] G. Chen, I. Roy, C. Yang, P. N. Prasad, "Nanochemistry and Nanomedicine for Nanoparticle-Based Diagnostics and Therapy" *Chem. Rev.* **2016**, *116*, 2826.
- [19] F. Hammerer, G. Garcia, S. Chen, F. Poyer, S. Achelle, C. Fiorini-Debuisschert, M. P. Teulade-Fichou, P. Maillard, "Synthesis and Characterization of Glycoconjugated Porphyrin Triphenylamine Hybrids for Targeted Two-Photon Photodynamic Therapy" *J. Org. Chem.* **2014**, *79*, 1406.
- [20] M. Gary-Bobo, Y. Mir, C. Rouxel, D. Brevet, I. Basile, M. Maynadier, O. Vaillant, O. Mongin, M. Blanchard-Desce, A. Morère, M. Garcia, J. O. Durand, L. Raehm, "Mannose-Functionalized Mesoporous Silica Nanoparticles for Efficient Two-Photon Photodynamic Therapy of Solid Tumors" *Angew. Chem. Int. Ed.* **2011**, *50*, 11425.
- [21] C. Zeng, W. Shang, X. Liang, X. Lieng, Q. Chen, C. Chi, Y. Du, C. Fang, J. Tian, "Cancer Diagnosis and Imaging-Guided Photothermal Therapy Using a Dual-Modality Nanoparticle" *ACS Appl. Mater. Interfaces* **2016**, *8*, 29232.
- [22] C. N. LaFratta, J. T. Fourkas, T. Baldacchini, R. A. Farrer, "Multiphoton Fabrication" *Angew. Chem. Int. Ed.* **2007**, *46*, 6238.
- [23] M. Jin, J. Xie, J. P. Malval, A. Spangenberg, O. Soppera, D. L. Versace, T. Leclerc, H. Pan, D. Wan, H. Pu, P. Baldeck, O. Poizat, S. Knopf, "Two-Photon Lithography in Visible and NIR Ranges Using Multibranch-Based Sensitizers for Efficient Acid Generation" *J. Mater. Chem. C* **2014**, *2*, 7201.
- [24] W. Zhou, S. M. Kuebler, K. L. Braun, T. Yu, J. K. Cammack, C. K. Ober, J. W. Perry, S. R. Marder, "An Efficient Two-Photon-Generated Photoacid Applied to Positive-Tone 3D Microfabrication" *Science* **2002**, *296*, 1106.
- [25] B. H. Cumpston, S. P. Ananthavel, S. Barlow, D. L. Dyer, J. E. Ehrlich, L. L. Erskine, A. A. Heikal, S. M. Kuebler, I. Y. Sandy Lee, D. McCord-Maughon, J. Qin, H. Röckel, M. Rumi, X.-L. Wu, S. R. Marder, J. W. Perry, "Two-Photon Polymerization Initiators for Three-Dimensional Optical Data Storage and Microfabrication" *Nature*, **1999**, *398*, 51.
- [26] S. Miao, Y. Zhu, H. Zhuang, X. Xu, H. Li, R. Sun, N. Li, S. Ji, J. Lu, "Adjustment of Charge Trap Number and Depth in Molecular Backbone to Achieve Tunable Multilevel Data Storage Performance" *J. Mater. Chem. C* **2013**, *1*, 2320.
- [27] F. Hao, X. Zhang, Y. Tian, H. Zhou, L. Li, J. Wu, S. Zhang, J. Yang, B. Jin, X. Tao, G. Zhou, M. Jiang, "Design, Crystal Structures and Enhanced Frequency-Upconverted Lasing Efficiencies of a New Series of Dyes from Hybrid of Inorganic Polymers and Organic Chromophores" *J. Mater. Chem.* **2009**, *19*, 9163.
- [28] S. Casa, M. Henary, "Synthesis and Applications of Selected Fluorine-Containing Fluorophores" *Molecules*, **2021**, *26*, 1160.
- [29] G. Chandra, B. Mahto, V. R. Singh, G. K. Mahato, U. Rani, "Fluorescent Fluorinated Materials: A Novel Material for Application in Photodynamic Therapy and Designing Chemical Sensors" *J. Photochem. Photobiol., C* **2024**, *60–61*, 100677.
- [30] C. Martinelli, G. M. Farinola, V. Pinto, A. Cardone, "Synthetic Aspects and Electro-Optical Properties of Fluorinated Arylenevinylens for Luminescence and Photovoltaics" *Materials* **2013**, *6*, 1205.
- [31] R. Berger, G. Resnati, P. Metrangolo, E. Weber, J. Hulliger, "Organic Fluorine Compounds: A Great Opportunity for Enhanced Materials Properties" *Chem. Soc. Rev.* **2011**, *40*, 3496.

## RESEARCH ARTICLE


- [32] C. Botta, E. Cariati, G. Cavallo, V. Dichiarante, A. Forni, P. Metrangolo, T. Pilati, G. Resnati, S. Righetto, G. Terraneo, E. Tordin, "Fluorine-Induced J-Aggregation Enhances Emissive Properties of a New NLO Push-Pull Chromophore" *J. Mater. Chem. C* **2014**, *2*, 5275.
- [33] N. Bauer, Q. Zhang, J. J. Rech, S. Dai, Z. Peng, H. Ade, J. Wang, X. Zhan, W. You, "The Impact of Fluorination on Both Donor Polymer and Non-Fullerene Acceptor: The More Fluorine, the Merrier" *Nano Res.* **2019**, *12*, 2400.
- [34] J. M. W. Chan, "Pentafluorosulfanyl Group: An Emerging Tool in Optoelectronic Materials" *J. Mater. Chem. C* **2019**, *7*, 12822.
- [35] G. J. Mohr, F. Lehmann, U.-W. Grummt, U. E. Spichiger-Keller, "Fluorescent Ligands for Optical Sensing of Alcohols: Synthesis and Characterization of *p*-*N,N*-Dialkylamino-Trifluoroacetylstilbenes" *Anal. Chim. Acta* **1997**, *344*, 215.
- [36] Y. Xu, S. Yu, Y. Wang, L. Hu, F. Zhao, X. Chen, Y. Li, X. Yu, L. Pu, "Ratiometric Fluorescence Sensors for 1,2-Diamines Based on Trifluoromethyl Ketones" *Eur. J. Org. Chem.* **2016**, *2016*, 5868.
- [37] N. Aknine, A. S. Klymchenko, "Push-Pull Fluorescent Dyes with Trifluoroacetyl Acceptor for High-Fidelity Sensing of Polarity and Heterogeneity of Lipid Droplets" *Anal. Chem.* **2024**, *96*, 13242.
- [38] G. Landelle, A. Panossian, F. Leroux, "Trifluoromethyl Ethers and -Thioethers as Tools for Medicinal Chemistry and Drug Discovery" *Curr. Top. Med. Chem.* **2014**, *14*, 941.
- [39] F. R. Leroux, B. Manteau, J. P. Vors, S. Pazenok, "Trifluoromethyl Ethers - Synthesis and Properties of an Unusual Substituent" *Beilstein J. Org. Chem.* **2008**, *4*, No. 13.
- [40] Z. Huang, S. Jia, C. Wang, E. Tokunaga, Y. Sumii, N. Shibata, "New Utility of Electrophilic Trifluoromethylthiolation Reagents for the Synthesis of a Variety of Triflones" *J. Fluor. Chem.* **2017**, *198*, 61.
- [41] C. Hansch, A. Leo, R. W. Taft, "A Survey of Hammett Substituent Constants and Resonance and Field Parameters" *Chem. Rev.* **1991**, *91*, 165.
- [42] K. N. Lee, Z. Lei, C. A. Morales-Rivera, P. Liu, M. Y. Ngai, "Mechanistic Studies on Intramolecular C-H Trifluoromethoxylation of (Hetero)arenes via OCF<sub>3</sub>-Migration" *Org. Biomol. Chem.* **2016**, *14*, 5599.
- [43] Z. Li, Z. Wu, W. Fu, P. Liu, B. Jiao, D. Wang, G. Zhou, X. Hou, "Versatile Fluorinated Derivatives of Triphenylamine as Hole-Transporters and Blue-Violet Emitters in Organic Light-Emitting Devices" *J. Phys. Chem. C* **2012**, *116*, 20504.
- [44] E. Ripaud, C. Mallet, M. Allain, P. Leriche, P. Frre, J. Roncali, "Extended Triphenylamine Conjugated Systems Derivatized by Perfluorophenyl Groups" *Tetrahedron Lett.* **2011**, *52*, 6573.
- [45] Y. Ban, L. Hao, Z. Peng, L. Sun, L. Teng, Y. Zhao, "Triphenylamine-Based Highly Active Two-Photon Absorbing Chromophores with Push-Pull Systems" *Chin. Chem. Lett.* **2023**, *34*, 107880.
- [46] S. P. McIlroy, E. Cló, L. Nikolajsen, P. K. Frederiksen, C. B. Nielsen, K. V. Mikkelsen, K. V. Gothelf, P. R. Ogilby, "Two-Photon Photosensitized Production of Singlet Oxygen: Sensitizers with Phenylene-Ethynylene-Based Chromophores" *J. Org. Chem.* **2005**, *70*, 1134.
- [47] E. Tatsi, V. Raglione, G. R. Ragno, S. Turri, G. Mattioli, F. Porcelli, D. Caschera, C. Botta, G. Zanotti, G. Griffini, "Luminescent Solar Concentrators Based on Environmentally Friendly Tripodal D-( $\pi$ -A)<sub>3</sub> Triarylamine Luminophores" *J. Mater. Chem. C* **2025**, *13*, 14465.
- [48] B. Kumari, S. P. Singh, R. Santosh, A. Dutta, S. S. Mallajosyula, S. Ghosal, S. Kanvah, "Branching Effect on Triphenylamine-CF<sub>3</sub> Cyanostilbenes: Enhanced Emission and Aggregation in Water" *New J. Chem.* **2019**, *43*, 4106.
- [49] P. Gautam, Y. Wang, G. Zhang, H. Sun, J. M. W. Chan, "Using the Negative Hyperconjugation Effect of Pentafluorosulfanyl Acceptors to Enhance Two-Photon Absorption in Push-Pull Chromophores" *Chem. Mater.* **2018**, *30*, 7055.
- [50] M. Fecková, M. Klikar, C. Vourdaki, I. Georgoulis, O. Pytela, S. Achelle, Z. Růžicková, M. Fakis, P. Beier, F. Bureš, "Selective Employment of Electronic Effects of the Pentafluorosulfanyl Group across Linear and Tripodal Push-Pull Chromophores with Two-Photon absorption" *Mater. Adv.* **2025**, *6*, 5713.
- [51] S. Körsten, G. J. Mohr, "Star-Shaped Tripodal Chemosensors for the Detection of Aliphatic Amines" *Chem. Eur. J.* **2011**, *17*, 969.
- [52] L. Porrès, O. Mongin, C. Katan, M. Charlot, T. Pons, J. Mertz, M. Blanchard-Desce, "Enhanced Two-Photon Absorption with Novel Octupolar Propeller-Shaped Fluorophores Derived from Triphenylamine" *Org. Lett.* **2004**, *6*, 47.
- [53] C. Le Droumaguet, O. Mongin, M. H. V. Werts, M. Blanchard-Desce, "Towards 'Smart' Multiphoton Fluorophores: Strongly Solvatochromic Probes for Two-Photon Sensing of Micropolarity" *Chem. Commun.* **2005**, 2802.
- [54] C. Rouxel, C. Le Droumaguet, Y. Macé, S. Clift, O. Mongin, E. Magnier, M. Blanchard-Desce, "Octupolar Derivatives Functionalized with Superacceptor Peripheral Groups: Synthesis and Evaluation of the Electron-Withdrawing Ability of Potent Unusual Groups" *Chem. Eur. J.* **2012**, *18*, 12487.

## RESEARCH ARTICLE

- [55] C. Le Droumaguet, A. Sourdon, E. Genin, O. Mongin, M. Blanchard-Desce, "Two-Photon Polarity Probes Built from Octupolar Fluorophores: Synthesis, Structure-Properties Relationships, and Use in Cellular Imaging" *Chem. Asian J.* **2013**, *8*, 2984.
- [56] M. Morita, S. Yamada, T. Konno, "Systematic Studies on the Effect of Fluorine Atoms in Fluorinated Tolanes on Their Photophysical Properties" *Molecules* **2021**, *26*, 2274.
- [57] K. E. Johannessen, M. A. L. Johansen, R. F. Einrem, L. J. McCormick McPherson, A. B. Alemayehu, S. M. Borisov, A. Ghosh, "Influence of Fluorinated Substituents on the Near-Infrared Phosphorescence of 5d Metalloporphyrins" *ACS Org. Inorg. Au* **2023**, *3*, 241.
- [58] D. Chen, E. Zysman-Colman, "Exploring the Possibility of Using Fluorine-Involved Non-Conjugated Electron-Withdrawing Groups for Thermally Activated Delayed Fluorescence Emitters by TD-DFT Calculation" *Beilstein J. Org. Chem.* **2021**, *17*, 210.
- [59] M. Klikar, D. Georgiou, I. Polyzos, M. Fakis, Z. Růžicková, O. Pytela, F. Bureš, "Triphenylamine-Based Fluorophores Bearing Peripheral Diazine Regioisomers. Synthesis, Characterization, Photophysics and Two-Photon Absorption" *Dyes Pigm.* **2022**, *201*, 110230.
- [60] M. Klikar, K. Seintis, I. Polyzos, O. Pytela, T. Mikysek, N. Almonasy, M. Fakis, F. Bureš, "Star-Shaped Push-Pull Molecules with a Varied Number of Peripheral Acceptors: An Insight into Their Optoelectronic Features" *ChemPhotoChem* **2018**, *2*, 465.
- [61] D. Cvejn, E. Michail, I. Polyzos, N. Almonasy, O. Pytela, M. Klikar, T. Mikysek, V. Giannetas, M. Fakis, F. Bureš, "Modulation of (Non)Linear Optical Properties in Tripodal Molecules by Variation of the Peripheral Cyano Acceptor Moieties and the  $\pi$ -Spacer" *J. Mater. Chem. C* **2015**, *3*, 7345.
- [62] J. Kulhánek, Z. Burešová, M. Klikar, L. Sdralias, A. Katsidas, O. Pytela, P. Pařík, A. Růžicka, M. Fakis, F. Bureš, "Synthesis, Photophysics and Two-Photon Absorption of Imidazole-Centred Tripodal Chromophores" *Phys. Chem. Chem. Phys.* **2024**, *26*, 20908.
- [63] D. Cvejn, E. Michail, K. Seintis, M. Klikar, O. Pytela, T. Mikysek, N. Almonasy, M. Ludwig, V. Giannetas, M. Fakis, F. Bureš, "Solvent and Branching Effect on the Two-Photon Absorption Properties of Push-Pull Triphenylamine Derivatives" *RSC Adv.* **2016**, *6*, 12819.
- [64] B. L. Edelbach, B. M. Pharoah, S. M. Bellows, P. R. Thayer, C. N. Fennie, R. E. Cowley, P. L. Holland, "An Expedient Synthesis of 2,4,6-Tris(trifluoromethyl)aniline" *Synthesis* **2012**, *44*, 3595.
- [65] S. Mori, N. Tsuamoto, T. Kasagawa, E. Nakano, S. Fujii, H. Kagechika, "Development of Boron-Cluster-Based Progesterone Receptor Antagonists Bearing a Pentafluorosulfanyl (SF<sub>5</sub>) Group" *Chem. Pharm. Bull.* **2019**, *67*, 1278.
- [66] Z. Liu, W. Wei, L. Xiong, Q. Feng, Y. Shi, N. Wang, L. Yu, "Selective and Efficient Synthesis of Trans-arylvinylboronates and Trans-hetarylvinylboronates Using Palladium Catalyzed Cross-Coupling" *New J. Chem.* **2017**, *41*, 3172.
- [67] T. J. Carter, R. Mohtadi, T. S. Arthur, F. Mizuno, R. Zhang, S. Shirai, J. W. Kampf, "Boron Clusters as Highly Stable Magnesium-Battery Electrolytes" *Angew. Chem. Int. Ed.* **2014**, *53*, 3173.
- [68] A. A. Isse, A. Gennaro, "Absolute Potential of the Standard Hydrogen Electrode and the Problem of Interconversion of Potentials in Different Solvents" *J. Phys. Chem. B* **2010**, *114*, 7894.
- [69] D. T. Sawyer, A. Sobkowiak, J. L. Roberts Jr. in *Electrochemistry for Chemists, 2nd edition*. Wiley-Interscience, New York, Chichester, **1995**, pp. 1–528.
- [70] O. Exner, S. Böhm, "Negative Hyperconjugation of Some Fluorine Containing Groups" *New J. Chem.* **2008**, *32*, 1449.
- [71] F. Bureš, O. Pytela, F. Diederich, "Solvent Effects on Electronic Absorption Spectra of Donor-Substituted 11,11,12,12-Tetracyano-9,10-anthraquinodimethanes (TCAQs)" *J. Phys. Org. Chem.* **2009**, *22*, 155.
- [72] A. M. Brouwer, "Standards for Photoluminescence Quantum Yield Measurements in Solution" *Pure Appl. Chem.* **2011**, *83*, 2213.
- [73] M. Klikar, I. V. Kityk, D. Kulwas, T. Mikysek, O. Pytela, F. Bureš, "Multipodal Arrangement of Push-Pull Chromophores: a Fundamental Parameter Affecting Their Electronic and Optical Properties" *New J. Chem.* **2017**, *41*, 1459.
- [74] S. K. Suresh, L. M. Ramachandran, A. Krishnan, C. V. Suneesh, "The Effect of –CF<sub>3</sub> Substitution Position on the Aggregation-Induced Emission, Solvatochromism and Mechanofluorochromism Properties of the Conjugated 9-Butyl-9H-carbazole Phenylacrylonitrile Derivatives" *J. Photochem. Photobiol., A* **2023**, *444*, 114985.
- [75] F. Bureš, "Fundamental Aspects of Property Tuning in Push-Pull Molecules" *RSC Adv.* **2014**, *4*, 58826.
- [76] P. Swiderek, M. Michaud, L. Sanche, "Vibronic Structure in the Low-Lying Singlet-Triplet Transitions of Benzene and Toluene" *J. Chem. Phys.* **1996**, *105*, 6724.
- [77] A. R. Nair, M. G. Mohan, C. Raksha, A. Sreekumar, P. Manoj, Y. C. S. Kumar, A. Sivan, "Unveiling the Dual-State Emissive Behaviour of 4,6-Diarylpurine-2-amines through a Plug-and-play Approach" *Sci. Rep.* **2024**, *14*, 29795.

## RESEARCH ARTICLE

- [78] Z. Shi, J. Davies, S. H. Jang, W. Kaminsky, A. K. Y. Jen, "Aggregation Induced Emission (AIE) of Trifluoromethyl Substituted Distyrylbenzenes" *Chem. Commun.* **2012**, 48, 7880.
- [79] M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, G. A. Petersson, H. Nakatsuji, X. Li, M. Caricato, A. V. Marenich, J. Bloino, B. G. Janesko, R. Gomperts, B. Mennucci, H. P. Hratchian, J. V. Ortiz, A. F. Izmaylov, J. L. Sonnenberg, D. Williams-Young, F. Ding, F. Lipparini, F. Egidi, J. Goings, B. Peng, A. Petrone, T. Henderson, D. Ranasinghe, V. G. Zakrzewski, J. Gao, N. Rega, G. Zheng, W. Liang, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, K. Throssell, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. J. Bearpark, J. J. Heyd, E. N. Brothers, K. N. Kudin, V. N. Staroverov, T. A. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. P. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, J. M. Millam, M. Klene, C. Adamo, R. Cammi, J. W. Ochterski, R. L. Martin, K. Morokuma, O. Farkas, J. B. Foresman, D. J. Fox, Gaussian@16W Software Package, Program for the Theoretical (TD-)DFT Calculations, Wallingford (USA), **2016**.
- [80] D. M. Chang, D. Y. Kwon, Y. S. Kim, "Heteroleptic Dual Acceptor Organic Dyes with Rhodanine-3-acetic Acid and Cyanoacrylic Acid" *Mol. Cryst. Liq. Cryst.* **2013**, 585, 100.
- [81] M. Fakis, V. Petropoulos, P. Hrobárik, J. Nociarová, P. Osuský, M. Maiuri, G. Cerullo, "Exploring Solvent and Substituent Effects on the Excited State Dynamics and Symmetry Breaking of Quadrupolar Triarylamine End-Capped Benzothiazole Chromophores by Femtosecond Spectroscopy" *J. Phys. Chem. B* **2022**, 126, 8532.
- [82] K. Seintis, Ç. Şahin, I. Sigmundová, E. Stathatos, P. Hrobárik, M. Fakis, "Solvent-Acidity-Driven Change in Photophysics and Significant Efficiency Improvement in Dye-Sensitized Solar Cells of a Benzothiazole-Derived Organic Sensitizer" *J. Phys. Chem. C* **2018**, 122, 20122.
- [83] C. Xu, W. W. Webb, "Measurement of Two-Photon Excitation Cross Sections of Molecular Fluorophores with Data from 690 to 1050 nm" *J. Opt. Soc. Am. B* **1996**, 13, 481.
- [84] N. S. Makarov, M. Drobizhev, A. Rebane, "Two-Photon Absorption Standards in the 550–1600 nm Excitation Wavelength Range" *Opt. Express* **2008**, 16, 4029.
- [85] X. Zeng, C. Gong, H. Guo, H. Xu, J. Zhang, J. Xie, "Efficient Heterogeneous Hydroboration of Alkynes: Enhancing the Catalytic Activity by Cu(0) Incorporated CuFe<sub>2</sub>O<sub>4</sub> Nanoparticles" *New J. Chem.* **2018**, 42, 17346.
- [86] A. Payet, B. Blondeau, J. B. Behr, J. L. Vasse, "Synthesis of 1,3-Disubstituted Cyclohexenes from Dienylethers: Via Sequential Hydrozirconation/Deoxygenative Cyclisation" *Org. Biomol. Chem.* **2019**, 17, 798.
- [87] M. Wu, C. Yan, D. Zhuang, R. Yan, "Metal-Free C-S Bond Formation in Elemental Sulfur and Cyclobutanol Derivatives: The Synthesis of Substituted Thiophenes" *Org. Lett.* **2022**, 24, 5309.
- [88] K. Itami, T. Nokami, Y. Ishimura, K. Mitsudo, T. Kamei, J.-I. Yoshida, "Diversity-Oriented Synthesis of Multisubstituted Olefins through the Sequential Integration of Palladium-Catalyzed Cross-Coupling Reactions. 2-Pyridyldimethyl(vinyl)silane as a Versatile Platform for Olefin Synthesis" *J. Am. Chem. Soc.* **2001**, 123, 11577.
- [89] M. H. Aukland, F. J. T. Talbot, J. A. Fernández-Salas, M. Ball, A. P. Pulis, D. J. Procter, "An Interrupted Pummerer/Nickel-Catalysed Cross-Coupling Sequence" *Angew. Chem. Int. Ed.* **2018**, 57, 9785.
- [90] J. Qu, C. T. Cao, C. Cao, "Determining the Excited-State Substituent Constants of Furyl and Thienyl Groups" *J. Phys. Org. Chem.* **2018**, 31, e3799.
- [91] A. Vasseur, J. Muzart, J. Le Bras, "Dehydrogenative Heck Reaction of Furans and Thiophenes with Styrenes under Mild Conditions and Influence of the Oxidizing Agent on the Reaction Rate" *Chem. Eur. J.* **2011**, 17, 12556.
- [92] L. U. Colmenares, R. S. H. Liu, "<sup>19</sup>F NMR Evidence for Restricted Rotation of the Retinyl Chromophore in Doubly Labeled Visual Pigment Analogs" *J. Am. Chem. Soc.* **1992**, 114, 6933.
- [93] R. Chen, L. U. Colmenares, J. R. Thiel, R. S. I. Liu, "Spiral Hexatrienes. The Hindered cis Isomer of Mini-carotene-3 and Hexakis-(2,2',4,4',6,6'-trifluoromethyl)stilbene" *Tetrahedron Lett.* **1994**, 35, 7177.
- [94] L. U. Colmenares, R. S. H. Liu, "Fluorinated Phenylrhodopsin Analogs. Binding Selectivity, Restricted Rotation and <sup>19</sup>F-NMR Studies" *Tetrahedron*, **1996**, 52, 109.
- [95] G. M. Sheldrick, SHELXL-97, Program for Crystal Structure Refinement, University of Göttingen, Göttingen (Germany), **2008**.
- [96] O. Pytela, OPChem, (n.d.), Program for Visualization of Structures, University of Pardubice, Pardubice (Czechia), **2023**.
- [97] O. Pytela, OPStat, (n.d.), Program for Mathematical and Statistical Calculations, University of Pardubice, Pardubice (Czechia), **2018**.

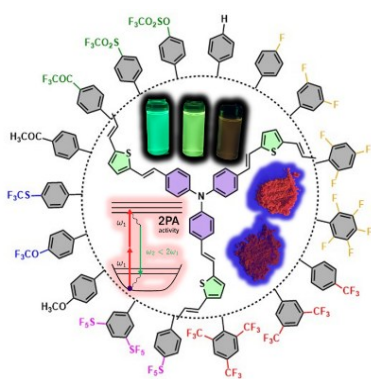

$C_3$ -symmetric D-( $\pi$ -D- $\pi$ -A) $_3$  fluorophores featuring central triphenylamine donor, polarizable 2,5-divinylthiophene linker, and a broad portfolio of fluorine-based substituents show tunable (non)linear optical properties.